

Magnetoresistance in High- T_c Superconductors: The Role of Vertex Corrections

Hiroshi KONTANI^{1,2}

¹*Theoretische Physik III, Elektronische Korrelationen und Magnetismus, Universität Augsburg, D-86135 Augsburg, Germany*

²*Department of Physics, Saitama University, 255 Shimo-Okubo, Urawa-city, 338-8570, Japan*

(February 1, 2008)

In high- T_c cuprates, the orbital magnetoresistance in plane ($\Delta\rho/\rho$) is anomalously enhanced at lower temperatures compared with conventional Fermi liquids, and thus Kohler's rule is strongly violated. Moreover, it should be noted that an intimate relation between $\Delta\rho/\rho$ and the Hall coefficient (R_H), $\Delta\rho/\rho \propto (R_H/\rho)^2$, holds well experimentally, and is called the "modified Kohler's rule". In this letter, we study this long-standing problem in terms of the nearly antiferromagnetic (AF) Fermi liquid. We analyze the exact expression for $\Delta\rho/\rho$ by including the vertex corrections (VC's) to keep the conservation laws, and find the approximate "scaling relation" $\Delta\rho/\rho \propto \xi_{AF}^4 \cdot \rho^{-2} \cdot H^2$ (ξ_{AF} being the AF correlation length.) in the presence of AF fluctuations. The factor ξ_{AF}^4 , which comes from the VC's for the current, gives the additional temperature dependence. By taking account of the relation $R_H \propto \xi_{AF}^2$ [Kontani et al., PRB 59 (1999) 14723.], we can naturally explain the modified Kohler's rule. In conclusion, based on the Fermi liquid theory, the famous *seemingly* non-Fermi liquid behaviors of R_H and $\Delta\rho/\rho$ in high- T_c cuprates are naturally understood on an equal footing.

Anomalous normal-state transport properties in high- T_c superconductors have attracted a great deal of attentions. For a wide range of temperatures, the resistivity (ρ), the Hall coefficient (R_H), and the in-plane magnetoresistance (MR, $\Delta\rho/\rho$) are approximately proportional to T , T^{-1} and T^{-4} , respectively [1–4]. These findings indicate the strong violation of Kohler's rule, that is, $R_H \propto \rho^0$ and $\Delta\rho/\rho \propto \rho^{-2}$. Kohler's rule is derived by the relaxation time approximation (RTA), assuming that the relaxation time ($\tau_{\mathbf{k}}$) is not very anisotropic. Irrespective of its quasiclassical approximation, Kohler's rule holds in various metals in general [5].

By definition, ρ , R_H , and $\Delta\rho/\rho$ are given by

$$\begin{aligned}\rho &= 1/\sigma_{xx} \\ R_H &= (\Delta\sigma_{xy}/H)/\sigma_{xx}^2, \\ \Delta\rho/\rho &= -\Delta\sigma_{xx}/\sigma_{xx} - (\Delta\sigma_{xy}/\sigma_{xx})^2,\end{aligned}\tag{1}$$

where σ_{xx} is the diagonal conductivity without the magnetic field $\vec{H}$ ($\vec{H} \parallel \hat{e}_z$). The Hall conductivity $\Delta\sigma_{xy}$ and the magnetoconductivity (MC) $\Delta\sigma_{xx}$ are of the order H^1 and H^2 , respectively.

The violation of Kohler's rule has been regarded as a serious test for the possible ground state of high- T_c cuprates. Until today, various authors have attempted to settle this issue in terms of a non-Fermi liquid picture, e.g., the spin-charge separation picture [6]. In recent years, several authors studied this problem in terms of the nearly antiferromagnetic (AF) Fermi liquid picture, and they ascribed the violation of Kohler's rule to the anisotropy of $\tau_{\mathbf{k}}$ based on the RTA [7,8]. However, they had to assume a huge anisotropy of $\tau_{\mathbf{k}}$ to produce the magnitude of the Hall coefficient. In that case, their model produced a MR too large to agree with experiments.

Recently, we studied the role of vertex corrections (VC's) on the Hall coefficient in high- T_c cuprates [9,10].

We found that the VC's for the current, which are dropped in the RTA, cause the Curie-Weiss-like behavior of R_H in the presence of AF fluctuations. The obtained results explain the experimental doping and temperature dependences of R_H satisfactorily [11]. Noteworthily, $R_H < 0$ observed in electron-doped compounds, which cannot be explained within the analysis by the RTA, is naturally reproduced in terms of the VC's [9,10].

In this letter, we introduce our theoretical study on the MR in high- T_c cuprates according to the expressions for the MR which is "exact" with respect to $O(\tau^2)$ [12]. We take account of all the VC's required by the Ward identity in order not to violate the conservation laws (i.e., the conserving approximation) [13]. Due to the VC's, the MR is strongly enhanced in the presence of AF fluctuations, which leads to the violation of Kohler's rule in high- T_c cuprates. Furthermore, the so-called "modified Kohler's rule", $\Delta\rho/\rho \propto (R_H/\rho)^2$, is well reproduced in our study in terms of the nearly AF Fermi liquid.

First, we calculate the self-energy $\Sigma_{\mathbf{k}}(\omega)$ by the fluctuation-exchange (FLEX) approximation, which is a kind of self-consistent perturbation theory with respect to U [14]. It is suitable for the analysis of the nearly AF Fermi liquid, and it has been applied to high- T_c cuprates [15] and κ -BEDT-TTF superconductors [16–18]. In the present study, we use 64×64 $\mathbf{k}$ -meshes and 512 Matsubara frequencies.

We study the square-lattice Hubbard model with on-site Coulomb interaction U . Figure 1 shows the non-interacting Fermi surface (FS) for $n = 0.85$. We put $(t, t', t''; U) = (1, -0.2, 0.15; 6.5)$ for YBCO, and $(1, -0.15, 0.05; 4.5)$ for LSCO, where t , t' and t'' are hopping integrals between the nearest neighbor, the second nearest and the third nearest, respectively [19]. As shown in ref. [9], $\gamma_{\mathbf{k}} \equiv \text{Im}\Sigma_{\mathbf{k}}(-i0) > 0$ takes a maximum [minimum] value around the hot-spot [cold-spot] in Fig. 1. The

portion of the FS near the cold-spot mainly contributes to the transport phenomena. We note that the anisotropy of $\gamma_{\mathbf{k}}$ is not very large according to the FLEX approximation; $\gamma_{\text{hot}}/\gamma_{\text{cold}} \lesssim 3$ for YBCO ($n=0.90$) at $T = 0.02$ [9]. This result is consistent with the recent analysis of the c -axis MR [20], or with ARPES measurements except in the pseudo spin-gap region.

Next, we study the transport coefficients by including the VC's for the current according to the conserving approximation. The expression for the conductivity without the magnetic field and the Hall conductivity are given by refs. [21] and [22], respectively:

$$\sigma_{xx} = \frac{e^2}{v_B} \oint_{\text{FS}} \frac{dk_{\parallel}}{|\vec{v}_{\mathbf{k}}|} v_{\mathbf{k}x} J_{\mathbf{k}x} \frac{1}{\gamma_{\mathbf{k}}}, \quad (2)$$

$$\Delta\sigma_{xy} = -H \cdot \frac{e^3}{4v_B} \oint_{\text{FS}} dk_{\parallel} |\vec{J}_{\mathbf{k}}|^2 \left(\partial\theta_{\mathbf{k}}^J / \partial k_{\parallel} \right) \frac{1}{\gamma_{\mathbf{k}}^2}, \quad (3)$$

$$J_{\mathbf{k}\mu} = \frac{1}{v_B} \oint_{\text{FS}} \frac{dk'_{\parallel}}{|\vec{v}_{\mathbf{k}'}|} \mathcal{T}(\mathbf{k}|\mathbf{k}') \frac{1}{\gamma_{\mathbf{k}'}} v_{\mathbf{k}'\mu} + v_{\mathbf{k}\mu}, \quad (4)$$

$$\mathcal{T}(\mathbf{k}|\mathbf{k}') \equiv \int \frac{d\epsilon}{4i} \mathcal{T}_{22}(\mathbf{k}, 0|\mathbf{k}', \epsilon), \quad (5)$$

where $v_B = (2\pi)^2$ and $\oint_{\text{FS}} dk_{\parallel}$ means the integration on the Fermi line. $\vec{v}_{\mathbf{k}} \equiv \vec{\nabla}(\epsilon_{\mathbf{k}}^0 + \text{Re}\Sigma_{\mathbf{k}}(0))$ is the quasiparticle velocity, and $\theta_{\mathbf{k}}^J = \tan^{-1}(J_{\mathbf{k}y}/J_{\mathbf{k}x})$. The total current $\vec{J}_{\mathbf{k}}$ is given by the solution of the Bethe-Salpeter equation, eq. (4). Here, the "reducible" vertex $\mathcal{T}_{22}(\mathbf{k}\epsilon|\mathbf{k}'\epsilon')$ in eq. (5) within the FLEX approximation is explained in ref. [9]. Note that $\vec{J}_{\mathbf{k}}$ is not parallel to $\vec{v}_{\mathbf{k}}$ due to $\mathcal{T}_{22}$ in general.

According to ref. [12], the expression for the MC with the VC's is given by

$$\Delta\sigma_{xx} \equiv \Delta\sigma_{xx}^a + \Delta\sigma_{xx}^b, \quad (6)$$

$$\Delta\sigma_{xx}^a = -H^2 \cdot \frac{e^4}{4v_B} \oint_{\text{FS}} \frac{dk_{\parallel}}{|\vec{v}_{\mathbf{k}}|} \{d_x(\mathbf{k})\}^2 \frac{1}{\gamma_{\mathbf{k}}},$$

$$\Delta\sigma_{xx}^b = -H^2 \cdot \frac{e^4}{4v_B} \oint_{\text{FS}} \frac{dk_{\parallel}}{|\vec{v}_{\mathbf{k}}|} d_x(\mathbf{k}) D'_x(\mathbf{k}) \frac{1}{\gamma_{\mathbf{k}}},$$

$$d_{\mu}(\mathbf{k}) = |\vec{v}_{\mathbf{k}}| \cdot \frac{\partial}{\partial k_{\parallel}} (J_{\mathbf{k}\mu}/\gamma_{\mathbf{k}}),$$

$$D'_{\mu}(\mathbf{k}) = \frac{1}{v_B} \oint_{\text{FS}} \frac{dk'_{\parallel}}{|\vec{v}_{\mathbf{k}'}|} \mathcal{T}(\mathbf{k}|\mathbf{k}') \frac{1}{\gamma_{\mathbf{k}'}} d_{\mu}(\mathbf{k}').$$

According to eqs. (3) and (6), $\Delta\sigma_{xy}$ and $\Delta\sigma_{xx}$ are of orders $O(\gamma^{-2})$ and $O(\gamma^{-3})$, respectively. If we drop all the VC's coming from $\mathcal{T}^I(\mathbf{k}|\mathbf{k}')$ in eqs. (2), (3) and (6), we obtain the results by the RTA with $\tau_{\mathbf{k}} = 1/2\gamma_{\mathbf{k}}$. We write them as σ_{xx}^{RTA} , $\Delta\sigma_{xy}^{\text{RTA}}$ and $\Delta\sigma_{xx}^{\text{RTA}}$, respectively.

Under the fourfold symmetry around the z -axis, $\Delta\sigma_{xx}^a$ in eq. (6) is rewritten as

$$\begin{aligned} \Delta\sigma_{xx}^a = & -H^2 \cdot \frac{e^4}{8v_B} \oint_{\text{FS}} dk_{\parallel} |\vec{v}_{\mathbf{k}}| \\ & \times \left[|\vec{l}_{\mathbf{k}}|^2 \left(\partial\theta_{\mathbf{k}}^J / \partial k_{\parallel} \right)^2 + \left(\partial|\vec{l}_{\mathbf{k}}| / \partial k_{\parallel} \right)^2 \right] \frac{1}{\gamma_{\mathbf{k}}} \end{aligned} \quad (7)$$

where $\vec{l}_{\mathbf{k}} = \vec{J}_{\mathbf{k}}/\gamma_{\mathbf{k}}$. In the same way, the MC without the VC's, $\Delta\sigma_{xx}^{\text{RTA}}$, is given by eq. (7) if we replace $\vec{l}_{\mathbf{k}} \rightarrow \vec{l}_{\mathbf{k}}^v \equiv \vec{v}_{\mathbf{k}}/\gamma_{\mathbf{k}}$ and $\theta_{\mathbf{k}}^J \rightarrow \theta_{\mathbf{k}}^v \equiv \tan^{-1}(v_{\mathbf{k}x}/v_{\mathbf{k}y})$. We note that eq. (6) is the simplified expression of the original one given in ref. [12], under the condition $\gamma_{\mathbf{k}}^* \ll T$. In the present numerical study, we use the original expression in ref. [12] to obtain more reliable results.

Figure 2 shows the obtained temperature dependence of $\Delta\rho/\rho$ for $T \geq 0.02$ (~ 100 K) by using the original expression of eq. (6). We also plot $(\Delta\rho/\rho)_{\text{MC-RTA}}$, which is given by replacing $\Delta\sigma_{xx}$ with $\Delta\sigma_{xx}^{\text{RTA}}$ in eq. (1). Thus, Fig. 2 means that the VC's increase the ratio $\Delta\sigma_{xx}/\Delta\sigma_{xx}^{\text{RTA}}$ as the temperature decreases. We will discuss the mechanism later in this letter.

Figure 3 shows the temperature dependence of the following coefficient for YBCO:

$$\zeta = (\Delta\rho/\rho) \cdot (\cot\theta_H)^2 = -\frac{\Delta\sigma_{xx} \cdot \sigma_{xx}}{(\Delta\sigma_{xy})^2} - 1, \quad (8)$$

where $\cot\theta_H = \sigma_{xx}/\Delta\sigma_{xy} = \rho/R_H$. The calculated ζ is almost T -independent for a wide range of temperatures, $0.02 \leq T \leq 0.10$, which is consistent with the "modified Kohler's rule" observed in high- T_c cuprates. Experimentally, ζ slightly depends on the doping; $\zeta \approx 1.5 \sim 1.7$ for YBCO [1], and $\zeta \approx 2 \sim 3$ for $\text{Ti}_2\text{Ba}_2\text{CuO}_{6+\delta}$ [3]. (Note that $\zeta = \Delta\rho = 0$ for an isotropic system.)

We also show the result of the RTA in Fig. 3, ζ_{RTA} , where all the VC's are neglected. As was pointed out in previous studies based on the RTA [8], ζ_{RTA} is too large to agree with experiments at low temperatures.

On the other hand, $\zeta_{\text{MC-RTA}}$ is given by eq. (8) by replacing $\Delta\sigma_{xx}$ with $\Delta\sigma_{xx}^{\text{RTA}}$. Considering that $\sigma_{xx} \sim \sigma_{xx}^{\text{RTA}}$ as shown in ref. [9], we obtain $\zeta_{\text{MC-RTA}} + 1 \sim (\zeta_{\text{RTA}} + 1) \cdot (\Delta\sigma_{xy}^{\text{RTA}}/\Delta\sigma_{xy})^2$. As shown in Fig. 3, $\zeta_{\text{MC-RTA}}$ is too small at low temperatures because $\Delta\sigma_{xy}$ is largely enhanced due to the VC's, which explains the Curie-Weiss-like behavior of R_H [9]. In conclusion, the modified Kohler's rule is well satisfied only when all the VC's for $\Delta\sigma_{xy}$ and $\Delta\sigma_{xx}$ are taken into account. Thus, the VC's play an essential role for the MR. We will discuss the reason for this later.

Here, we discuss why the modified Kohler's rule is well satisfied by taking the VC's into account. In YBCO, the spin-susceptibility given by the FLEX approximation is qualitatively described as

$$\chi_{\mathbf{q}}(\omega) = \chi_Q(1 + \xi_{\text{AF}}^2(\mathbf{q} - \mathbf{Q})^2 - i\omega/\omega_{\text{sf}})^{-1}, \quad (9)$$

where $\mathbf{Q} = (\pi, \pi)$, ξ_{AF} is the AF-correlation length, and $\chi_Q \propto \omega_{\text{sf}}^{-1} \propto \xi_{\text{AF}}^2$. According to the SCR theory [23] or the renormalization group study [24], $\xi_{\text{AF}}^2 \propto (T + c)^{-1}$ in two-dimensional systems, which is observed in high- T_c cuprates around the optimum doping [25]. This relation is also reproduced well by the FLEX approximation [15].

As shown in ref. [9], $\mathcal{T}^I(\mathbf{k}; \mathbf{k}') \propto iT^2 \text{Im}\chi_{\mathbf{k}-\mathbf{k}'}(\omega)/\omega|_{\omega \rightarrow 0}$ due to the Maki-Thompson term, which is essential when

AF fluctuations are strong. According to eq. (9), we see that the "momentum-derivative of $\mathcal{T}_{22}$ " causes a factor proportional to $\xi_{\text{AF}}^2 \propto T^{-1}$. This suggests that $\Delta\sigma_{xy}$ and $\Delta\sigma_{xx}$ are enhanced by ξ_{AF}^2 and ξ_{AF}^4 according to eqs. (3) and (6), which will cause the breakdown of Kohler's rule in the presence of AF fluctuations.

Now we discuss $\Delta\sigma_{xx}$ in more detail: According to the analysis in § V of ref. [9], $\left(\frac{\partial\theta_{\mathbf{k}}^j}{\partial k_{\parallel}}\right) \propto \xi_{\text{AF}}^x \cdot \left(\frac{\partial\theta_{\mathbf{k}}^v}{\partial k_{\parallel}}\right)$ and $x \approx 2$ around the cold spot in YBCO or LSCO. To be precise, x may deviate from 2 somehow due to the ξ_{AF} -dependence (or T -dependence) of the shape of the FS, which is prominent in high- T_c cuprates [9]. As a result, the first term of eq. (7) is proportional to ξ_{AF}^{2x} .

The second term of eq. (7) vanishes in an isotropic system. In the case of YBCO, it is small in our numerical calculation because $|\vec{v}_{\mathbf{k}}|$ on the FS is rather isotropic in YBCO. Although it is enhanced at lower temperatures as $\gamma_{\mathbf{k}}$ becomes anisotropic, it is still small in YBCO because $|\vec{l}_{\mathbf{k}}| = |\vec{v}_{\mathbf{k}}/\gamma_{\mathbf{k}}|$ is not very anisotropic according to the FLEX approximation for $n \leq 0.9$ [9].

According to a similar analysis in § V of ref. [9], we can show that $\Delta\sigma_{xx}^b$ in eq. (6) is also proportional to ξ_{AF}^{2x} [26]. However, its absolute value is quite small in YBCO in the present calculation, although this may be accidental. In conclusion, in the case of YBCO, only the first term of eq. (7) is dominant for $\Delta\sigma_{xx}$ which is enhanced by ξ_{AF}^{2x} .

Next, we show the temperature dependence of ζ in the case of LSCO in Fig. 4. ζ in LSCO is much larger than that in YBCO, particularly for $n = 0.8$. This is because the second term of eq. (7) becomes important as the anisotropy of $|\vec{v}_{\mathbf{k}}|$ on the FS is larger in LSCO. In particular, the FS at $n = 0.8$ is very close to the van-Hove singular point $(\pi, 0)$. Experimentally, $\zeta \approx 13.6$ for the slightly over-doped sample, $x = 0.17$, and it increases (decreases) as the doping increases (decreases) [2]. Thus, our calculation results are consistent with those of experiments.

According to the present numerical study, the second term of eq. (7) is approximately proportional to the first term which is proportional to $\xi_{\text{AF}}^{2x} \cdot \gamma_{\text{cold}}^{-3}$. Moreover, $\Delta\sigma_{xx}^b$ in eq. (6) also makes an important contribution to the MR in LSCO, which is proportional to ξ_{AF}^{2x} . In Fig. 4, ζ in LSCO shows weak T -dependence, which mainly comes from the second term of eq. (7) [27]. However, its T -dependence is much smaller than that of ζ_{RTA} or $\zeta_{\text{MC-RTA}}$, as shown in Fig. 4.

In summary, we obtain the following relations by taking the VC's into account in the nearly AF Fermi liquid:

$$\begin{aligned}\Delta\sigma_{xy} &\propto \xi_{\text{AF}}^x \cdot \gamma_{\text{cold}}^{-2}, \\ \Delta\sigma_{xx} &\propto \xi_{\text{AF}}^{2x} \cdot \gamma_{\text{cold}}^{-3},\end{aligned}\quad (10)$$

and $x \sim 2$. Because $\sigma_{xx} \propto \xi_{\text{AF}}^0 \cdot \gamma_{\text{cold}}^{-1}$, we obtain the relations $\Delta\rho/\rho \propto \xi_{\text{AF}}^{2x} \cdot \gamma_{\text{cold}}^{-2}$ and $\zeta \propto \xi_{\text{AF}}^0 \cdot \gamma_{\text{cold}}^0 \approx \text{const.}$, which explain why the "modified Kohler's rule" is satisfied in high- T_c cuprates in general for a wider range of

temperatures.

Figure 5 shows that the obtained scaling behavior for YBCO, $\Delta\rho \cdot \rho \propto R_{\text{H}}^2 \propto \xi^{2x}$ and $x \approx 1.5$, which is consistent with eq. (10) well. This obtained result directly means that $\Delta\sigma_{xx} \propto T^{-4.5}$ or $\Delta\rho/\rho \propto T^{-3.5}$ because the relations $\chi_Q(0) \propto \xi_{\text{AF}}^2 \propto T^{-1}$ and $\gamma_{\text{cold}} \propto T^{-1}$ hold well for $T \geq 0.02$ in the present FLEX approximation. This result is consistent with that of the experiment on 90 K-YBCO [2]. We note that in the present study $R_{\text{H}}(T = 0.02)/R_{\text{H}}(T = 0.2)$ is about 3.8 for YBCO ($n = 0.9$), and about 4 for LSCO ($n = 0.85$).

In this letter, we mainly focus on systems around the optimum doping weight above the pseudo spin-gap temperature (T^*), where the modified Kohler's rule holds well experimentally. In our numerical study, $\xi_{\text{AF}} \lesssim 3a$ for $n \leq 0.9$ in YBCO (a being the lattice spacing), which is consistent with experiments [9]. Moreover, $\gamma_{\text{hot}}/\gamma_{\text{cold}}$ is suppressed to ~ 3 because of the feedback effect in the FLEX approximation. It is an important theoretical (and experimental) future problem to analyze the MC in a heavily under-doped region where $\xi_{\text{AF}} \sim 10$ will be realized. Finally, we discuss the MR in the pseudo spin-gap region. Experimentally, $\Delta\rho/\rho$ starts to increase much faster than T^{-4} below T^* . This behavior can be explained if we assume that $\gamma_{\text{hot}}/\gamma_{\text{cold}} \gg 1$ is realized below T^* because the second term of eq. (7) becomes much larger. This assumption is supported by a recent study of the pseudo spin-gap phenomena in terms of the strong superconducting fluctuations below T^* [28].

In summary, we studied the anomalous behaviors of the MR in high- T_c cuprates in terms of the Fermi liquid theory. To go beyond the RTA, the role of the VC's is analyzed by the conserving approximation based on the exact expression for $\Delta\rho/\rho$. By virtue of the VC's, the modified Kohler's rule is satisfactorily reproduced in the presence of AF fluctuations. The obtained value of $\zeta = \Delta\rho \cdot \rho / R_{\text{H}}^2$ is consistent with experimental value both for YBCO and LSCO. In conclusion, the VC's are essential for reproducing the *seemingly* non-Fermi liquid behaviors of both R_{H} and $\Delta\rho/\rho$ in high- T_c on an equal footing.

The author is grateful to D. Vollhardt, K. Yamada and Y. Ando for valuable comments and discussions.

-
- [1] J. M. Harris, Y. F. Yan, P. Mati, N. P. Ong, P. W. Anderson, T. Kimura and K. Kitazawa: Phys. Rev. Lett. **75** (1995) 1391.
 - [2] T. Kimura, S. Miyasaka, H. Takagi, K. Tamasaku, H. Eisaki, S. Uchida, K. Kitazawa, M. Hiroi, M. Sera, and N. Kobayashi: Phys. Rev. B **53** (1996) 8733.
 - [3] A. W. Tyler, Y. Ando, F. F. Balakirev, A. Passner, G. S. Boebinger, A. J. Schofield, A. P. Mackenzie, and O. Laborde: Phys. Rev. B **57** (1998) R728.

- [4] Y. Ando and T. Murayama : Phys. Rev. B **60** (1999) R6991.
- [5] J. M. Ziman: *Electrons and Phonons* (Clarendon Press, ltd., Oxford, 1960).
- [6] P. W. Anderson: Phys. Rev. Lett. **67** (1991) 2092.
- [7] B. P. Stojković and D. Pines: Phys. Rev. B **55** (1996) 857.
- [8] L. B. Ioffe and A. J. Millis: Phys. Rev. B **58** (1998) 11631.
- [9] H. Kontani, K. Kanki and K. Ueda.: Phys. Rev. B **59** (1999) 14723.
- [10] K. Kanki and H. Kontani: J. Phys. Soc. Jpn. **68** (1999) 1614.
- [11] J. Takeda, T. Nishikawa, and M. Sato: Physica C **231** (1994) 293.
- [12] H. Kontani: to appear in Phys. Rev. B. **64** (2001) (cond-mat/0011238).
- [13] G. Baym and L. P. Kadanoff: Phys. Rev. **124** (1961) 287.
- [14] N. E. Bickers and S. R. White: Phys. Rev. B **43** (1991) 8044
- [15] T. Dahm and L. Tewordt: Phys. Rev. B **52** (1995) 1297.
- [16] H. Kino and H. Kontani: J. Phys. Soc. Jpn. **67** (1998) 3691.
- [17] H. Kondo and T. Moriya: J. Phys. Soc. Jpn. **67** (1998) 3695.
- [18] J. Schmalian: Phys. Rev. Lett. **81** (1998) 4232.
- [19] In contrast to ref. [9], here we put $|t'| > |t''|$ both for YBCO and LSCO because it would be more realistic. The results of the present work are also valid for parameters (t, t', t'', U) which are used in ref. [9].
- [20] K. G. Sandeman and A. J. Schofield: cond-mat/0007299.
- [21] G. M. Eliashberg : Sov. Phys. JETP **14** (1962), 886.
- [22] H. Kohno and K. Yamada: Prog. Theor. Phys. **80** (1988) 623.
- [23] T. Moriya, Y. Takahashi, and K. Ueda: J. Phys. Soc. Jpn **59** (1990) 2905.
- [24] A. J. Millis: Phys. Rev. B **48** (1993) 7183.
- [25] A. Goto, T. Shimizu, P. V. P. S. S. Sastry and J. Schwartz: Phys. Rev. B **59** (1999) R14169.
- [26] H. Kontani : in preparation.
- [27] Experimentally, ζ shows some T -dependence in LSCO, particularly for $n \leq 0.8$.
- [28] e.g., Y. Yanase and K. Yamada: to appear in J. Phys. Soc. Jpn. **70** (2001) (cond-mat/0103214).

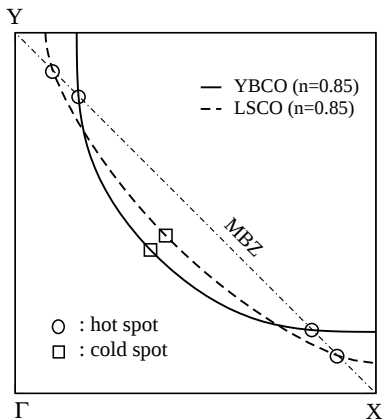


FIG. 1.

The noninteracting FS for YBCO and for LSCO. On the FS, $\gamma_{\mathbf{k}}$ takes the maximum [minimum] value around the hot-spot [cold-spot] (see ref. [9]).

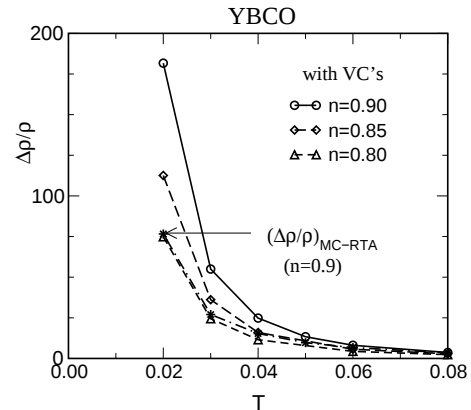


FIG. 2.

Temperature dependence of $\Delta\rho/\rho$ for YBCO with full VC's. We see that $(\Delta\rho/\rho)_{\text{MC-RTA}}$ is smaller, which means that the VC's for $\Delta\sigma_{xx}$ enhance the MR.

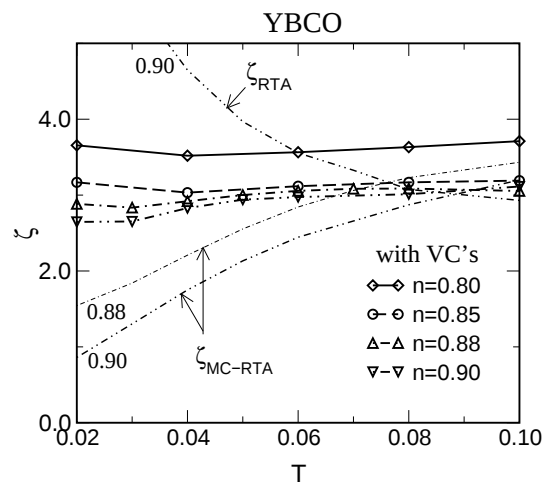


FIG. 3.

Calculated $\zeta = \Delta\rho \cdot \rho / R_H^2$ for YBCO with full VC's for $0.02 \geq T \geq 0.1$ ($T = 100\text{K} \sim 500\text{K}$). The modified Kohler's rule $\zeta = \text{const.}$ holds well only if all the VC's are taken into account.

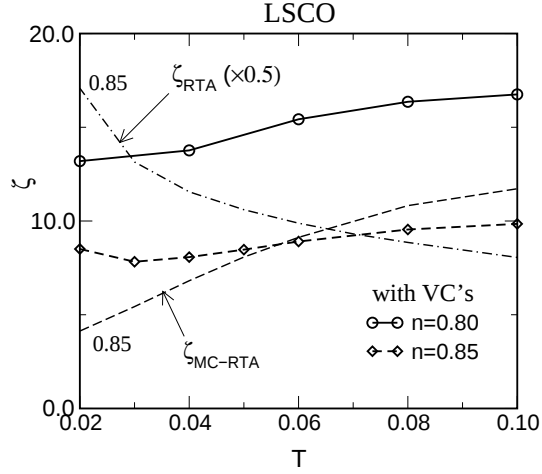


FIG. 4.

Temperature dependence of ζ for LSCO with full VC's.

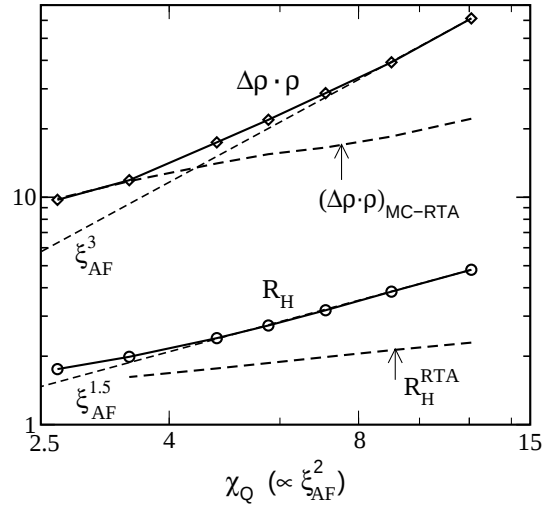


FIG. 5.

Scaling behaviors for YBCO ($n = 0.9$); $\Delta\rho \cdot \rho \propto R_H^2 \propto \xi_{\text{AF}}^{2x}$, which means $x \approx 1.5$. This plot is for $T = 0.02 \sim 0.08$ ($\chi_Q = 12 \sim 2.6$). We stress that the RTA fails to reproduce the scaling behavior.